

Improving Zonal Isolation in Casing Annuli Susceptible to Shallow Water Flows (Case Study)

¹M Asim Saeed, ²Babar Shahzad

^{1,2}*Department of Petroleum and Gas Engineering, Dawood University of Engineering and Technology*

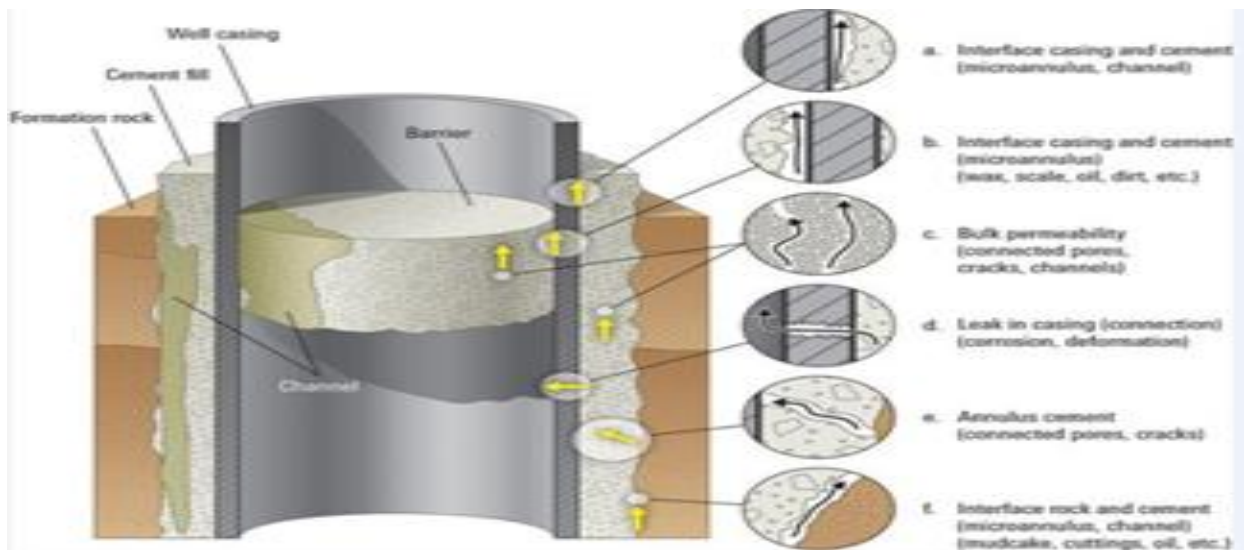
Abstract—The essential factor in cement setting is the transition of cement slurry to a solid phase and invasion of fluid during this time period intercepts in achieving a proper cement job. Shallow and highly pressurized water zones have been identified in the area of study. The water flows from these zones through the cement to the surface, thus addressing well control hazards and environmental issues. There are various characteristics that define a baseline for a cement to have, to prevent the water percolation through it while setting. The key role resides in thickening time and static gel strength development of the cement slurry.

The foamed cement, particle size distribution (PSD) cement and microsphere cements have been known to have successfully mitigated the water percolation problem. Each solution has its own merits and demerits thus cost is a crucial factor in selecting one of these solutions.

Two cement slurries were proposed named A-Slurry#1 and A-Slurry#2, these slurries have transition time 2 minutes and 1 minutes respectively as compared to the 13 minutes transition time of case study slurry. The short transition time of the proposed slurries and other characteristics establishes this slurry as a potential candidate to overcome the shallow water flow problems concurrent in the field.

I. INTRODUCTION

Cementing a well is the basic and one of foremost operations in drilling and completing a well. Primarily a well cementing is applied to restrict inter-zonal flows and aiding the well casing by providing necessary support. Some problems concurrent due to an improper cement operation are casing corruptions, casing-cement interface flow, cement defect and mud channels, cement-formation interface flows, fracture flows, micro annuli in cement sheath, thread leaks as shown below[1]:

Figure 1 Improper cement outcomes^[1]

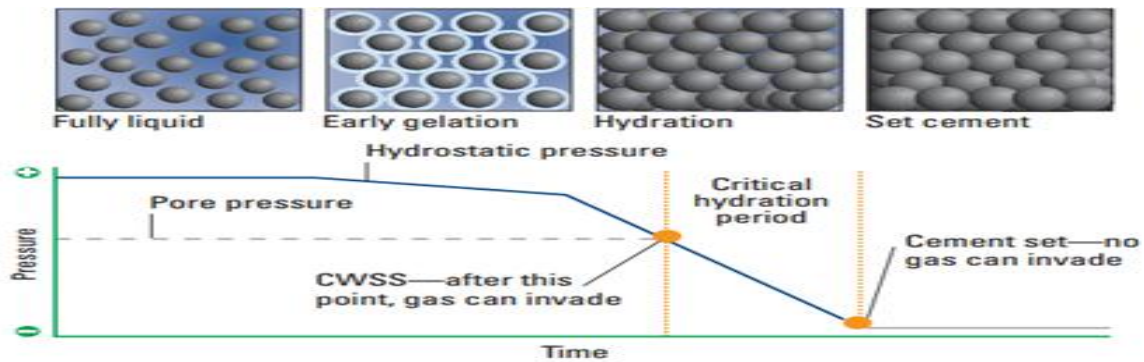
These problems arise due to improper cement design or challenging formation properties and conditions, such as low fracture gradient formations, shallow water flow zones, loss of circulation zones, thief zones, unstable shale, shallow gas formations and many more. The area of study named “CASE-X” consists of shallow water flow (SWF) zones that are highly pressurized due to connection with an outcrop source and geological complexity of the formations present. The troublesome SWF zones are present at various depths.

II. CASE-X CEMENTING PROBLEMS

The SWF zones have their effects in the exploration and production phases. These can result during the drilling and even at the time of abandonment of the well. There are two major problems faced when encountering an SWF zone consists of cement zonal isolation and surface casing vent flows and sustained Casing Pressures. The surface casing vent flows and sustained casing pressures are emanates of poor zonal isolation subjected under shallow water or gas flows. The problems occurred are further explained as following:

2.1 CEMENT ZONAL ISOLATION

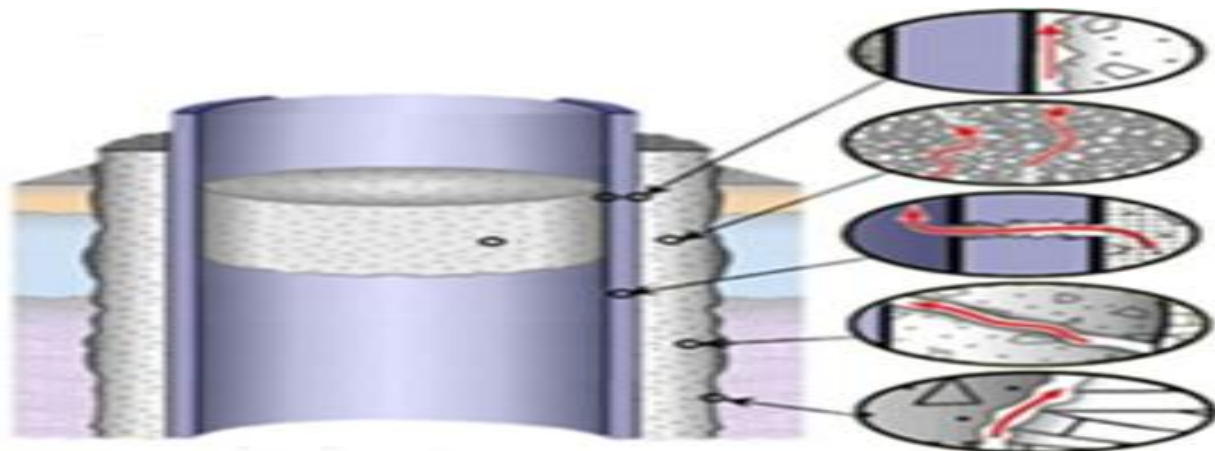
The hydration of slurry with respect to time results in phase transition from soft gel like material to a solid hard material known as Transition time. Transition time is the measure of time from which cement goes from 100 lbf/100 sq. ft (48 Pa) to 500 lbf/100 sq.ft (240 Pa). During the liquid phase of the cement slurry the hydrostatic pressure exerted by this slurry is higher than that of the pore pressure of the adjacent formation. The critical wall shear stress (CWSS) defined as the point where critical hydration period (CHP) begins. At this point cement starts hardening to provide a self-support and the slurry column can no longer transmit hydrostatic pressure. The hydrostatic pressure of the remaining water in the porous and permeable cement must balance with the pore pressure from the formation.

Figure 2 Cement setting process ^[4]

Since SWF zones have a very high pore pressure, at this point (CHP) the water encroaches into the cement sheath because it has lost its hydrostatic pressure due to hardening and also is not hard enough to resist the water flow. This water flow creates microannuli's and percolates through the cement sheath.

2.2 SURFACE CASING VENT FLOW AND SUSTAINED CASING PRESSURE

Surface casing vent flows are the flow of gas or any liquid or their combinations out of the casing annulus and often referred to as internal migration. Surface casing vent flows are a result of improper zonal isolation of cementing process, which has induced various flows through the systems. The flow can be through the interface of casing –cement, cement-formation, casing leaks, formation fractures, microannuli in cement sheath.

Figure 3 Interface flows ^[6]

Sustained Casing Pressure (SCP) is an aftereffect of surface casing vent flow that occurs when the flowing fluid doesn't find a flow path towards surface and due to high source pressure it accumulates in the casing annulus. The accumulation of such fluid results in pressure buildup that results in a pressurized annulus. The buildup pressures are bleed-off routinely but have to be permanently shut off prior to well plug and abandonment.

III. CEMENT SOLUTIONS ACROSS THE GLOBE

There have been various SWF zones related problem reported and mitigated with cement slurries by addition of different kinds of additives, but each solution has been constrained towards the situation and conditions present. From all those studies an understanding has been developed for cement slurry to have the following characteristics to mitigate a shallow water zone.

Table 1 Requisite characteristics

PROPERTY	PRESCRIPTION
Free water	Zero free water
Transition time	As low as possible and inversely dependent on pressure of SWF zone
Density	Sufficient to induce overbalanced hydrostatic pressure
Compressive strength	Adequate to support wellbore
Rheology	Sufficient for effective annular displacement

The cements that are widely accepted to have the potential to mitigate SWF zones are as following:

3.1 MICROSPHERE CEMENT

This cement is a strong and lightweight cement containing microspheres composed of silica, flashy shell or other water-soluble substances. These microspheres consist of nitrogen or CO₂ or another specified chemical. These slurries are typically used for cementing intermediate casing where low permeability cements are mandatory due to weak formations containing any migrating fluid.

To mitigate SWF zones microsphere cement consists of microspheres filled with super absorbent polymers (SAP) that swell in contact with water and help in plugging the microannuli's created due to percolation of water in the cement sheath [11].

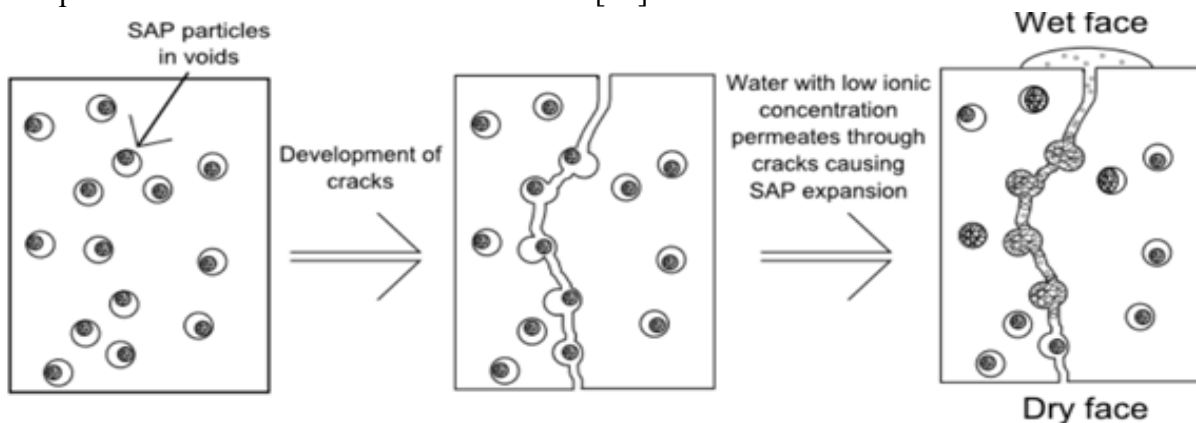


Figure 4 SAP swelling mechanism [10]

3.2 FOAM CEMENT

The foam cements consist of base cement mixed with a gas by compressors and Nitrogen gas is often used to form the foam slurry. The foam slurry is applicable when the density of conventional cement cannot be reduced without deferring the required properties. The cement is utilized in fields of low fracture gradients, low temperatures and Shallow water/gas flow zones.

The mechanism of the foam cement in preventing the migration of fluids during critical hydration period is similar to that of Microsphere cement using pressured microspheres. The compressible property of the cement allow slight compensate for volumetric changes due to cement hydration and leak-off. The viscous nature of the foam resists the flow of annular fluids. These properties combined are used to prevent migration of shallow flows into the cement sheath.

A case study of foam cementing by waheed et.al 2002 [14], a field consisted of many wells but five of them in the vicinity that were prone to shallow water flows The wells are named as V,W,X,Y,Z. Due to water flow problems encountered on well V and W the other wells sharing the same problem were foam cemented and no water flows were encountered. The casing cement design summary is given below:

Well Name	Lead Cement	Tail Cement	Spacer
V	12 ppg gel cement	15 ppg neat cement	Sea water
W	12 ppg gel cement	15 ppg neat cement	Sea water
X	12.1 to 13.4 ppg foam cement	15 ppg neat cement	Sea water
Y	10.8 to 12.6 ppg foam cement	15 ppg neat cement	Sea water
Z	9.8 to 11.8 ppg foam cement	15 ppg neat cement	Sea water

Table 2 Foam cement case

3.3 PARTICLE SIZE DISTRIBUTION (PSD)

Particle size distribution (PSD) cements are based on the concept of solid particle size adjustment. The proper particle size distribution increases the compressive strength of the cement and reduces its porosity and permeability independent to the slurry density

The PSD cement was successfully applied to a field facing SWF zone problems as reported by Landbo T. et.a[32]. The properties of slurry consisted of zero free water, fluid loss 18mL/30min and transition time of 19.6 minutes.

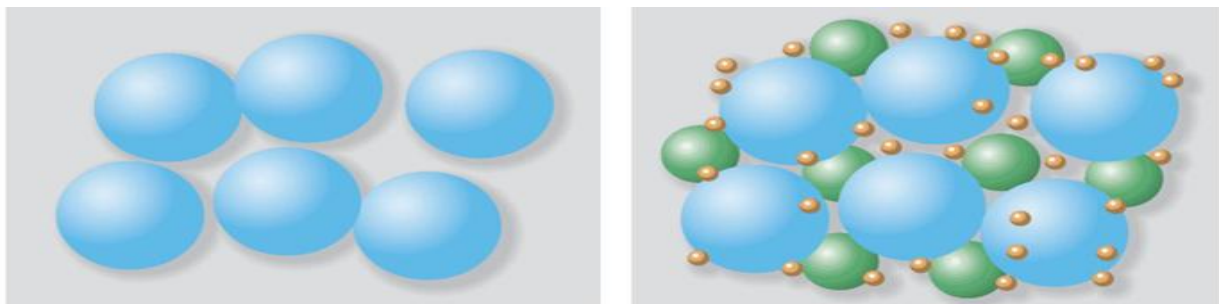


Figure 5 PSD cement structure [14]

IV. METHODOLOGY

In this study, a series of various cement design with their additives would be compared with the cement design applied in the SWF zone from case study. The properties to be compared are enlisted below density, plastic viscosity, yield point, thickening time and free fluid.

The cement designs to be compared consist of Case-X slurry, PSD slurry from a field test¹ and a proposed slurry named A-Slurry. The additives of PSD and Case-X slurry are subject to proprietary matter, but the additives of A-slurry are given below:

Table 3 A-slurry composition

ADDITIVES	A-SLURRY	
	#1	#2
Fresh Water (L)	47.5	43.8
Defoamer (L)	0.01	0.01
Fumed Silica suspension (L)	-	10
Synthetic Fluid loss additives (Kg)	0.6	0.6
Synthetic retarder (Kg)	0.3	0.7
Expansion aid (dry blended) (Kg)	5	7.5
Class G (Kg)	100	100

The A-slurry basically focuses on preventing fluid migration by addition of expansive agents and latent hydraulic materials. These materials form a dense matrix that reduces the permeability and has a higher resistance to fluid percolations

V. PROPERTIES OF CEMENT SLURRIES

The properties measured of the A-slurry are given in the table below:

Table 4 A-Slurry properties

Property	A-SLURRY	
	#1	#2
Density (ppg)	15.8	15.8
Thickening Time (hrs:min)		
30 Bc		
70 Bc	2:54	6:03

¹ Malakai Deepwater, Block G, Offshore Sabah, Malaysia

100 Bc	3:02 3:04	6:04 6:05
Rheology at mix		
300	218	107
200	150	78
100	78	45
60	48	30
30	26	18
6	7	6
3	4	5
Plastic viscosity	210	93
Yield Point (lbf/100ft ²)	8	14
Free Water %	0	0
API Fluid Loss (ml/30min)	52	48
UCA at 81.6°C 3000 psi		
Time to 50 psi	6:38	15:02
Time to 500 psi	8:09	16:21
24 hrs	2205	2650
48 hrs	2900	3075
72 hrs	3200	3282

The properties of Case-X slurry are given below:

Table 5 Case-X slurry properties

Properties	Case X Slurry
Density (ppg)	15.8
Plastic Viscosity (cp)	40.5
Yield point (lbf/100ft ²)	20.1
Thickening Time @70 Bc	5:45
Transition time from 70 to 100Bc	13 minutes
Free fluid (mL/250mL)	0

The properties of PSD slurry are given as below:

Properties	PSD Cement
Density (ppg)	12.0
Plastic Viscosity (cp)	233.2
Yield point (lbf/100ft ²)	12.1
Thickening Time (hr:mm) @70Bc	12:24
Free fluid (mL/250mL)	0
24-hour compressive strength (psi)	516

Table 6 PSD slurry properties

VI. COMPARISON OF CEMENT SLURRIES

The properties of the Case-X slurry with the PSD slurry and with A-Slurry#1 and A-Slurry#2 are compared as following:

Table 7 Comparison of all slurries

Properties	PSD Cement	Cement A slurry#1	Cement A slurry#1	Case X slurry
Density (ppg)	12.0	15.8	15.8	15.8
Plastic Viscosity (cp)	233.2	210	93	40.5
Yield point (lbf/100ft ²)	12.1	8	14	11.6
Thickening Time (hr:mm) @70 (Bc)	12:24	3:02	6:04	5:45
Transition time 70 to 100 (Bc)	NA	2 minutes	1 minute	13 minute
Free fluid (mL/250mL)	0	0	0	0
24-hour compressive strength psi	516	2205	2650	NA

The discussion for each property is given as following:

- Plastic viscosity: The plastic viscosity of Cement-A slurries and PSD are greater than that of Case-X cement, it determines that they are enough viscous to prevent water percolation when the cement is in liquid phase.
- Yield point: The yield point of all the slurries in the table compared have similar yield point except for slurry 2 that has a lower yield point.
- Thickening Time: The thickening time of Cement A-Slurry#1 is lower than others, which can help in setting the cement earlier than others because it has lower critical hydration period than others. The transition time of Cement Slurry A is very low as compared to Case X slurry that defines how lower its critical hydration period would be, lower critical hydration period means that the slurry forms a solid sheath faster to prevent percolation of water.
- Free Fluid: There was no free fluid in all the slurries compared being a requisite factor for any cement slurry to mitigate shallow water flow zones requires.
- Compressive Strength: The compressive strength development for Cement slurry A-Slurry#1 and A-Slurry#2 are greater than that of PSD cement ensuring a good structural support.

VII. CONCLUSION

The Cement Slurry A shows prominent results that are necessary for a cement system to mitigate shallow water flows to allow a proper cement job execution. The conclusion for the topic considering the requirement and slurry properties analyzed are given as following:

- Shorter thickening time transitions allow the cement to hydrate fast such that it has a minimum critical hydration period.
- The cement slurry has a rapid compressive strength build thus it can be concluded that the transition of slurry from liquid phase to solid is fast resulting in lower critical hydration period.
- The results indicate that the cement is quick setting cement and the slurry is very economic as compared to the foam cement and PSD cement.
- In contrast to PSD cement and foamed cement, the experimental slurry has no technical complexity or any high cost job executions.

The A-Slurry#1 and A-Slurry#2 showcased more prominent results in comparison to the PSD slurry and Case-X slurry.

VIII. RECOMMENDATIONS

The cement slurry proposed has prominent results but there is still room for improvement and advancements. Due to unavailability of some results the permeability and static gel strength development could not be discussed thus questioning the credibility of the cement to be used for mitigating for SWF zones in real field scenarios.

But the results from thickening time of cement seem that the use of cement slurry is provident for preventing shallow water flows.

ABBREVIATIONS

CHP Critical hydration period
CWSS Critical wall shear stress
PSD Particle size distribution
SCP Sustained casing pressure
SCVF Surface casing vent flow
SWF Sallow water flow zones

REFERNCES

- [1] Carrol, S. C. Review: Role of chemistry, mechanics, and transport on well integrity in CO₂ storage environments. *International Journal of Greenhouse Gas Control*-49, 149-160. 2016.
- [2] Alberty, Hafle et.al; "Mechanisms of Shallow Waterflows and Drilling Practices for Intervention" *SPE Drill & Completion*, Vol 14, No. 2, June 1999.
- [3] J.S Eaton Review Article: "Influence of Ancient Thrust Faults on the Hydrogeology of the Blue Ridge Province"

- [4] Jessica Geonawan et.al; “Overcoming shallow hazards in Deepwater Malikai Batch-set Top-hole sections with Engineered trimodal particle-size distribution cements”, OTC-26409-MS presented at OTC Kuala Lumpur Malaysia 22-25 March 2016.
- [5] Kellingray Darryl; “Cementing-Planning for Success to Ensure Isolation for the Life of the Well”, SPE-112808-DLS, SPE Distinguished Lecture Series (pp. 1-34). Houston: Society of Petroleum Engineers (SPE) Foundation 2007.
- [6] Michael A. Celia et.al; Review Article: “Quantitative estimation of CO₂ leakage from geological storage” 7th International Conference on Greenhouse Gas Control technologies 5-September 2004, Vancouver, Canada.
- [7] Bachu Stefan et.al; “Assessing the potential for CO₂ leakage particularly through wells from geological storage sites Carbon Sequestration and Its Role in the Global Carbon Cycle” Geophysical Monograph Series 183:203-216, January 2009.
- [8] Schlumberger Glossary “Sustained Casing Pressure”
- [9] Mark Van de Velden; “Expandable Sleeve Isolate Shallow Aquifers” SPE 120684, SPE Middle East Oil and Gas show and conference, Kingdom of Bahrain, 15-18 march 2009.
- [10] Lee H.X.D., Wong H.S., Buenfeld N.R.; “Potential of superabsorbent polymer for self - sealing cracks in concrete” Adv. Appl. Ceram. 2010; 109:296–302.
- [11] Bu Yuhuan, Liu Huajie; “Self-plugging Technology of Microcrack with Water in Cement Sheath” OTC-26367-MS, OTC Kuala Lumpur Malaysia 22-25 March 2016.
- [12] Pegasus Vertex, Inc. white paper issue “Design and Simulation of Foamed Cement Jobs”
- [13] Kopp Kevin et.al; “Foamed Cement vs Conventional Cement for Zonal Isolation- Case Histories” SPE-62895 Annual Technical Conference and Exhibition held in Dallas, Texas, October 1-4.
- [14] Arshad Waheed, Mark Cockram and Mahdy Bahr; “Foam Cementing Controls Deepwater Shallow Flow in the East Mediterranean” SPE-74402, SPE International Petroleum Conference and Exhibition Mexico 2002.
- [15] Chengwen Wang, Ruihe Wang, Yuhuan Bu and Weidong Zhou; “ A unique Cement Slurry Overcoming Low Temperature, Shallow Water/Gas Flows in Deepwater Cementing” SPE/IADC-125405, SPE/IADC Middle East Drilling Technology Conference and Exhibition Manam, Bahrain 2009.
- [16] Pedersen Rikke et.al; “A Successful Field Experience: Shallow Water Flow- How to Avoid the Need for Additional Casing String”, SPE-112716 ATCE Florida, USA 2008.
- [17] “Guidelines for Abandonment of Wells”, Oil and Gas UK, Issue 5 July 2015.
- [18] Hekelaar Stephan et.al; “Increasing Reliability of Cutting/Pulling in a single trip”
- [19] Obodozie et.al; “Eliminating sustained Casing Pressure in Well Abandonment” OTC-26432, OTC Kuala Lumpur Malaysia 22-25 March 2016.
- [20] Office of Fossil Energy “DOE Foamed-Cement Research Is Changing Industry”, US department of energy, July 18,2016

- [21] Rufat Mammadbayli, Jon Greener, Dale Doherty, Jose Reyes and Patrico Torres; “Foamed Cement successfully applied in Shallow Water Environment in Caspian Sea” IAD Conference 2016.
- [22] Dijilali Sahnoun et.al; “Cut and Cap Process for Surface Casing Vent Flow Repair and Prevention”, Advance in cement research No. 25, 9-12 Jan 1995.
- [23] Justness et. al; “Porosity of oil well cement slurries during setting, Advance in cement research No. 25, 9-12 Jan 1995.
- [24] E.D. Dalrymple et.al; “A Selective Water Control Process”, SPE 24330, SPE Rocky Mountain Regional Meeting held in Casper, Wyoming, May 18-21, 1992
- [25] P, Skalle, “Cementing Problems When Setting Casing Through Porous Gas & Water Bearing Formation”, Oil Gas European Magazine 1/2002
- [26] Backe, P.Skalle et.al; “Shrinkage of Oil Well Cement Slurries” The Journal of Canadian Petroleum Technology, Volume 37, No. 9 ,September 1998.
- [27] Baumgarte, Thiercelin and Klaus; “Case studies of Expanding Cement To Prevent Microannular Formation” SPE 56535, SPE ATC Houston, Texas 1999.
- [28] Bermea Vargas, Taoutaou et.al; “A case study of Flexible/Expandable and Self-Healing Cement fo Ensuring Zonal Isolation in a Shallow, Hydraulically fractured Gas Well, Onshore Thailand”, SPE/IADC-173065-MS, IADC conference and Exhibition London, UK 2015.
- [29] W.J. Clarke and A.C McNally; “Ultrafine Cement for Oilwell Cementing”, SPE-25868, SPE Denver, CO, USA 1993.
- [30] Todd B ELLIS and Edgar Paul R. Acorda;” Mitigation of Deepwater Shallow Hazards with Simplified Cement System: South China Sea Case Study” IPTC-16592, IPTC Beijing, China 2013.
- [31] S.Z Elzeghaty, Holger Kinzel, R.L. Colvard; “Cement Seal Units Eliminate Interzonal Communication” SPE-105770, 15th SPE Middle East Oil and Gas Show and Conference, Kingdom of Bahrain 2007.
- [32] T. Landbo Opseth et.al; “Curing Shallow Water Flow in a North Sea Exploration Well Exposed to Shallow Gas” SPE-124607, SPE Offshore Europe Oil and Gas Conference and Exhibition Aberdeen, UK 2009.
- [33] Krishna Ravi, Ewout N. Biezem, C. Lightford, Ashley Hibbert and Chris Greaves; “Deepwater Cementing Challenges” SPE-56534, SPE ATC Houston, Texas USA 1999.
- [34] B.R. Reddy, Feng Liang and Rocky Fitzgerald; “Self-Healing Cements that Heal without Dependence on Fluid Contact” SPE-121555, SPA International Symposium on Oilfield Chemistry The Woodlands, Texas USA 2009.
- [35] Ronnie Faul, B.R. Reddy et.al; “Next-Generation Cementing Systems to Control Shallow Water Flow” OTC-11977, OTC Houston, Texas, USA 2000.
- [36] Jim O’Leary, Juan Carlos Flores, Paulo Rubinstein and Greg Garrison; “Cementing Deepwater, Low Temperature Gulf Of Mexico Formations Prone to Shallow Flows”IADC/SPE -87161, IADC/SPE Drilling Conference Dallas, Texas, USA 2004.